



检测报告

TEST REPORT

编号 (No.) : UTS17050115R03

报告日期 (Report Date) : 2017/05/19

委托单位/Client : 中良通信科技(苏州)有限公司
ZhongLiang Communication Technology Ltd.

地址/Address : 苏州市相城区望亭镇新华路 68 号
Xinhua Industrial Park, Wangting Town, Suzhou, Jiangsu Province, China

以下测试样品由申请人提供及确认:

The following sample(s) was/were submitted and identified on behalf of the client as:

样品名称/Sample Name : 光纤槽道及配件

样品信息/Sample Information : 规格/Spec.: 宽/Wide*高/High

(50*50 mm

100*100 mm

120*100 mm

150*100 mm

240*100 mm

300*100 mm

340*100 mm

360*100 mm)

样品材质/Material: PC(80%)+ABS(20%)工程塑料

测试数量/Test Quantity : 1 PC

接收日期/Receiving Date : 2017/05/05

检测周期/Test Period : 2017/05/05-2017/05/18

检测要求/Test Request : 参见下一页/Please refer to next page(s).

检测方法/Test Method(s) : 参见下一页/Please refer to next page(s).

检测结果/Test Result(s) : 参见下一页/Please refer to next page(s).



批准
Approved by

刘贵宁

授权签字人

审核
Reviewed by

肖利

肖利

检测
Tested by

陈林

陈林

Page 1 of 9

This test report is issued by the company subject to its General Conditions of Service printed overleaf or available on request. Attention is drawn to the limitations of liability, underwriting and arbitration policies defined therein. The results shown in this Test report refer only to the sample(s) tested unless otherwise stated. This test report shall not be reproduced, except in full, without written approval of the Company. 本报告按本公司所制定之通用服务条款所编制发放。请注意本报告首页背面之此条款, 本公司之义务、责任、管辖权均有明确规定, 该条款也可向本公司索取。除非另有说明, 本报告仅对来样负责, 未经许可, 不得部分复制本报告。

江苏省优联检测技术服务有限公司

地址: 苏州市吴中区越溪街道北官渡路50号3幢

电话 (Tel): +86(0)512-66358200

UNITED TESTING SERVICES (JIANGSU) CO., LTD.

Address: Building 3, No.50 Beiguandu Road, Wuzhong Zone, Suzhou, Jiangsu, China

传真 (Fax): +86(0)51266358088

www.uts.com.cn



检测报告

TEST REPORT

编号 (No.) : UTS17050115R03

报告日期 (Report Date) : 2017/05/19

检测环境/Test Environment:

环境温度/Ambient Temperature: (23±2)°C

环境湿度/Ambient Humidity: (55±10)%RH

检测设备/Test Equipment:

设备名称 Name of Test Equipment	设备编号 Equipment No.	校准/Calibration	
		上次校准/Last Cal.	预计校准/Due Cal.
汽车内饰件燃烧试验机/Car Inner Decoration Combustion Testing Machine	F-1-006	2017/02/24	2018/02/23
恒温恒湿试验箱 /Temperature & humidity test chamber	R-1-039	2017/01/12	2018/01/11
恒温恒湿试验箱 /Temperature & humidity test chamber	R-1-088	2017/02/20	2018/02/19
高温老化试验箱 /Burn-in Chamber	R-1-017	2017/02/20	2018/02/19
绝缘电阻测试仪 /Insulation resistance tester	R-1-043	2017/02/20	2018/02/19
振动试验系统 /Vibration testing system	R-1-068	2017/02/20	2018/02/19
数显卡尺 /Digital Caliper	M-1-027	2017/02/20	2018/02/19

检测结果/Test Result(s):

1. 外观/Appearance

检测方法/Test Method: Q/320507 TDB01-2011 4.3

客户要求 /Customer Requirement	检测结果 /Test Results	结论 /Conclusion
<p>样品表面应平整、光滑、洁净、无明显凹凸现象，无飞边、暗泡、收缩、凹陷或机械损伤等缺陷；$\Delta E < 2$。</p> <p>/The surface of the sample should be flat, smooth, clean, no obvious bump phenomenon, no flash, dark bubble, shrink, sag or mechanical damage and other defects.</p>	<p>样品表面应平整、光滑、洁净、无明显凹凸现象，无飞边、暗泡、收缩、凹陷或机械损伤等缺陷。/The surface of the sample should be flat, smooth, clean, no obvious bump phenomenon, no flash, dark bubble, shrink, sag or mechanical damage and other defects.</p> <p>L=75.01; a=14.83; b=78.95</p>	符合/PASS



检测报告

TEST REPORT

编号 (No.) : UTS17050115R03

报告日期 (Report Date) : 2017/05/19

2. 尺寸/Size

检测方法/Test Method: Q/320507 TDB01-2011 4.4

客户要求 /Customer Requirement		检测结果 /Test Results	结论 /Conclusion
壁厚/Walk thickness	3(1±5%)mm	2.8 mm	符合/PASS
长度/Length	380(1±0.15%) mm	378 mm	符合/PASS
曲率半径/Radius of curvature	≥ 40 mm	40 mm	符合/PASS

3. 挠度的最大变形量/Maximum amount of deformation of the deflection

检测方法/Test Method: Q/320507 TDB01-2011 4.6

支持跨距/Span: 1.5 m; 额定载荷/Rated load: 350 N.

客户要求 /Customer Requirement	检测结果 /Test Results	结论 /Conclusion
≤ 10 mm	7 mm	符合/PASS

4. 撞击/Impact

检测方法/Test Method: Q/320507 TDB01-2011 4.7

光纤槽经 1 kg 重物, 从 1000 mm 高度垂直跌落撞击。/Fiber groove withstand 1 kg weights, from 1000 mm high degree of vertical drop impact.

客户要求 /Customer Requirement	检测结果 /Test Results	结论 /Conclusion
无裂痕或脆断现象。 /No cracks or brittle fracture phenomenon emerged on the surface of sample.	试验后, 无裂痕或脆断现象。 /After the test, no cracks or brittle fracture phenomenon emerged on the surface of sample.	符合/PASS



检测报告

TEST REPORT

编号 (No.) : UTS17050115R03

报告日期 (Report Date) : 2017/05/19

5. 承重试验/Bearing Test

检测方法/Test Method: Q/320507 TDB01-2011 4.8

客户要求 /Customer Requirement	检测结果 /Test Results	结论 /Conclusion
光纤槽应能承受 800 N 的静载荷, 无裂痕或脆断现象。/The fiber groove should be able to withstand 800 N of static load, no cracks or brittle fracture phenomenon.	承受 800 N 静载荷, 无裂痕或脆断现象。 /Under 800 N loading, no cracks or brittle fracture phenomenon emerged on the surface of sample.	符合/PASS

6. 电气性能/Electrical Performance

检测方法/Test Method: Q/320507 TDB01-2011 4.9

6.1 抗电强度/Dielectric Strength

客户要求 /Customer Requirement	检测结果 /Test Results	结论 /Conclusion
恒定湿热试验前: AC4200V、50 Hz, 1 min 无闪烁或击穿现象。/Before damp heat test: AC4200V, 50 Hz, 1 min no flicker or breakdown.	恒定湿热试验前: AC4200V、50Hz 1min 无闪烁或击穿现象。/Before damp heat test: AC4200V、50Hz 1min no flicker or breakdown.	符合/PASS
恒定湿热试验后: AC4200V、50 Hz, 1 min 无闪烁或击穿现象。/After damp heat test: AC4200V, 50 Hz, 1 min no flicker or breakdown.	恒定湿热试验后: AC4200V、50Hz 1min 无闪烁或击穿现象。/after damp heat test: AC4200V、50Hz 1min no flicker or breakdown.	符合/PASS

6.2 绝缘电阻/Insulation Resistance

客户要求 /Customer Requirement	检测结果 /Test Results	结论 /Conclusion
恒定湿热试验前/Before damp heat test: $\geq 20 \text{ M}\Omega$	恒定湿热试验前: $\geq 20 \text{ M}\Omega$ / Before damp heat test: $\geq 20 \text{ M}\Omega$	符合/PASS
恒定湿热试验后/After damp heat test: $\geq 5 \text{ M}\Omega$	恒定湿热试验后: $\geq 5 \text{ M}\Omega$ /after damp heat test: $\geq 5 \text{ M}\Omega$	符合/PASS



检测报告

TEST REPORT

编号 (No.) : UTS17050115R03

报告日期 (Report Date) : 2017/05/19

7. 燃烧试验/Flame Test

样品处理/Conditioning:

23±2°C, 50±5%RH的环境中处理48h。 / 23±2°C and 50±5 %, RH for 48 hours.

检测方法/Test Method: GB/T 2408-2008 《塑料 燃烧性能的测定 水平法和垂直法》 /Plastics - Determination of burning characteristics - Horizontal and vertical test

试验方法/Procedure:

将灯焰移到样品的底部10±1 mm处, 停留10±0.5s, 然后将灯焰移开, 在移开试验火焰后, 测量任一样品上火焰燃烧的持续时间 t_1 。 /Apply the flame centrally to the middle point of the bottom edge of the specimen so that the top of the burner is 10±1 mm below that point of the lower end of the specimen, and maintain it at that distance for 10±0.5 seconds, immediately withdraw the burner and simultaneously commence measurement of the after flame time t_1 .

样品上的火焰燃烧一经停止后, 应立即在同一样品上施加火焰, 灯焰距离残余样品底部10±1 mm, 停留10±0.5s, 然后将灯焰移开, 在移开试验火焰后, 测量任一样品上火焰燃烧的持续时间 t_2 , 并在 t_2 结束后测量余燃的持续时间 t_3 。 / As soon as after flaming of the specimen ceases, place the burner again under the specimen and maintain the burner at a distance of 10±1 mm from the remaining major portion of the specimen for an additional 10±0.5 seconds, after this application of the flame to the specimen, immediately remove the burner and simultaneously commence measurement of the after flame time, t_2 , and the afterglow time, t_3 .

在每一组剩余的四个样品上应重复进行上述一系列规定的试验。 /Repeat the test to the remaining four specimens.

试验数据/Test Data:

	t_1 (s)	t_2 (s)	t_3 (s)	$\Sigma(t_1+t_2)$ (s)	t_2+t_3 (s)	燃烧至夹持处 Burnout up to the holding clamp	是否引燃脱脂棉 Ignite cotton or not
1#	1	1	0	10	1	否/No	否/No
2#	1	1	0		1	否/No	否/No
3#	1	1	0		1	否/No	否/No
4#	1	1	0		1	否/No	否/No
5#	1	1	0		1	否/No	否/No
结果/Result	V-0 级/V-0 Grade						
客户要求/Customer requirement	V-0 级/V-0 Grade						
结论/Conclusion	符合/PASS						



检测报告

TEST REPORT

编号 (No.) : UTS17050115R03

报告日期 (Report Date) : 2017/05/19

等级判据/Classifications:

标准/Criteria	V-0	V-1	V-2
每个独立的样品燃烧持续的时间, t_1 或 t_2 / After flame time for each individual specimen t_1 or t_2 ,	$\leq 10s$	$\leq 30s$	$\leq 30s$
对任意处理组的五个样品的总的燃烧持续时间, $\Sigma(t_1+t_2)$ / Total after flame time for any condition set, $\Sigma(t_1+t_2)$,	$\leq 50s$	$\leq 250s$	$\leq 250s$
在第二次火焰施加后, 每个独立的样品燃烧持续时间和灼热燃烧时间, t_2+t_3 / After flame plus afterglow time for each individual specimen after the second flame application, t_2+t_3 ,	$\leq 30s$	$\leq 60s$	$\leq 60s$
是否允许任一样品持续燃烧和灼热燃烧到夹持样品的夹持处? / After flame or afterglow of any specimen up to the holding clamp?	否/No	否/No	否/No
是否允许燃烧颗粒或滴落物引燃脱脂棉? / Cotton indicator ignited by flaming particles or drops?	否/No	否/No	是/Yes

8. 耐高温性能/High Temperature Performance

检测方法/Test Method: Q/320507 TDB01-2011 4.11.1

检测条件/Test Condition: $(55\pm 2)^\circ\text{C}$, 2 h.

客户要求 /Customer Requirement	检测结果 /Test Results	结论 /Conclusion
无明显的变形、变色等缺陷。/No obvious deformation, discoloration and other defects.	$(55\pm 2)^\circ\text{C}$ 、2h 耐高温性试验后, 试样无明显的变形、变色等缺陷。/ $(55 \pm 2)^\circ\text{C}$, after 2 hours of high temperature test, sample not have a obvious deformation, discoloration, and other defects.	符合/PASS

9. 耐低温性能/Low Temperature Performance

检测方法/Test Method: Q/320507 TDB01-2011 4.11.2

检测条件/Test Condition: $(-25\pm 2)^\circ\text{C}$, 2 h.

客户要求 /Customer Requirement	检测结果 /Test Results	结论 /Conclusion
无明显的变形、变色等缺陷。/No obvious deformation, discoloration and other defects.	$(-25\pm 2)^\circ\text{C}$ 、2h 耐低温性试验后, 试样无明显的变形、变色、裂纹等缺陷。/ $(-25 \pm 2)^\circ\text{C}$, after 2 hours of low temperature test sample no obvious deformation, discoloration, crack and other defects.	符合/PASS



检测报告

TEST REPORT

编号 (No.) : UTS17050115R03

报告日期 (Report Date) : 2017/05/19

10. 耐高温高湿性能/Temperature and Humidity Performance

检测方法/Test Method: Q/320507 TDB01-2011 4.11.3

检测条件/Test Condition: (30±2)°C, 85%RH, 48 h.

客户要求 /Customer Requirement	检测结果 /Test Results	结论 /Conclusion
样品外观不应出现异常, 其内外表面之间的绝缘电阻不小于 5 MΩ。/the appearance of samples should not be abnormal, the insulation resistance between its inner and outer surface is not less than 5 MΩ.	(30±2)°C、RH 85%、48h 湿热试验后, 试样外观没有出现异常, 其内外表面之间的绝缘电阻不小于 5MΩ。/(30±2)°C、RH 85% after 48 hours damp heat test. the appearance of the sample not be abnormal, the insulation resistance between its inner and outer surfaces is not less than 5MΩ.	符合/PASS

11. 振动试验/Vibration Test

检测方法/Test Method: Q/320507 TDB01-2011 4.11.4

检测条件/Test Condition:

客户要求 /Customer Requirement	检测结果 /Test Results	结论 /Conclusion
样品完整、表面及零部件不应有机械性损伤, 紧固件不应松脱。/the sample should be complete, the surface and parts should not be mechanical injury, fasteners should not be loose.	根据 GB/T 3873 中“A10 公路运输”的试验要求, 试验结束后: 产品完整、表面及零部件没有机械性损伤, 紧固件无松脱。/ According to the testing requirements of GB / T 3873 in the A10 road transport ", after the test: the sample complete, the surface and parts not be mechanical injury, fasteners not be loose.	符合/PASS



检测报告

TEST REPORT

编号 (No.) : UTS17050115R03

报告日期 (Report Date) : 2017/05/19

12. 老化/Aging


检测方法/Test Method: Q/320507 TDB01-2011 4.12

检测条件/Test Condition: (55±2)°C, 240 h; 室温/R.T., 4 h; (-25±2)°C, 2 h.

客户要求 /Customer Requirement	检测结果 /Test Results	结论 /Conclusion
无裂痕或脆断现象。 /No cracks or brittle fracture phenomenon emerged on the surface of sample.	将试样置于高温箱内, 在(55±2)°C温度下保持 240h, 取出后, 在室温下冷却 4h, 然后再放入(-25±2)°C低温箱内保持 2h。取出后立即进行冲击试验, 无裂痕或脆断现象。/ The sample is placed in the high temperature chamber (55 ± 2)°C temperature for 240h, after removing cooled at room temperature for 4h, then put (-25 ± 2)°C low temperature inside to keep 2h. Removed immediately after the impact test, no cracks or brittle fracture phenomenon.	符合/PASS

13. 材质分析/Material Composition

客户要求 /Customer Requirement	检测结果 /Test Results	结论 /Conclusion
主含量为 PC /The main content for PC	聚碳酸酯(PC), 87%(匹配度) /Polycarbonate	符合/PASS

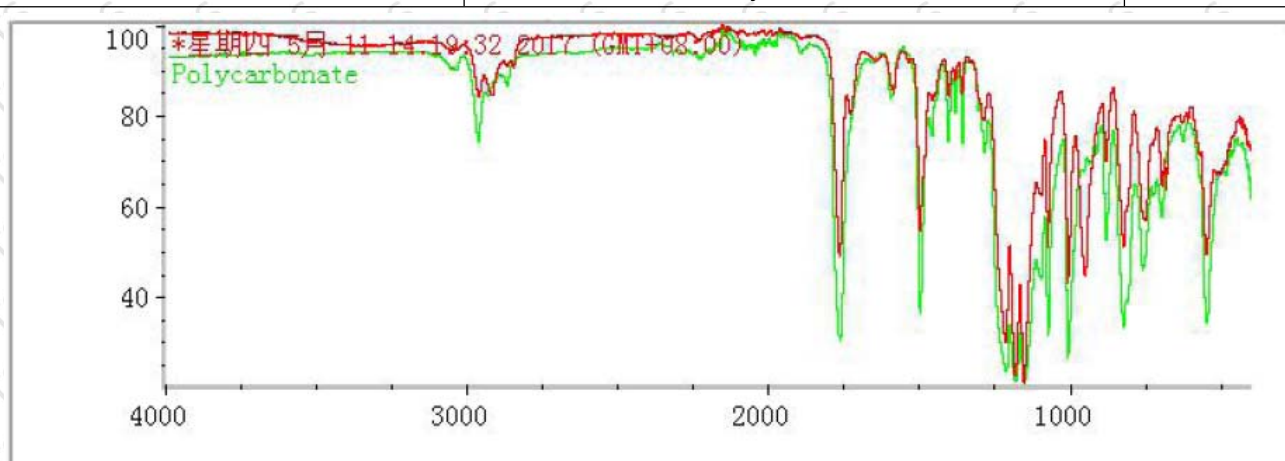

库号	匹配度	化合物名称	谱库名称
1 229	87.97	CD ROM (data side)	Common Materials
2 43	87.72	Polycarbonate	HR Spectra Polymers and Plasticizer



检测报告

TEST REPORT

编号 (No.) : UTS17050115R03

报告日期 (Report Date) : 2017/05/19

样品照片/Sample Photo(s):



图 1 试验前

Fig.1 Before the test

.....报告结束/End of Report.....